

Pipe joint assemblies and fittings for high-density polyethylene (PE-HD) pressure pipes
Injection-moulded fittings for butt welding
Dimensions

DIN
16963
Part 6

Rohrverbindungen und Rohrleitungsteile für Druckrohrleitungen aus Polyethylen hoher Dichte (PE-HD);
Fittings aus Spritzguß für Stumpfschweißung, Maße

Dimensions in mm

1 Field of application


This standard specifies requirements for injection-moulded¹⁾ polyethylene (PE-HD) fittings to be joined with pipes as specified in DIN 8074 by heated tool butt welding as described in DIN 1910 Part 3 or DVS 2207 Part 1. These fittings shall also comply with the requirements specified in DIN 16963 Part 5.

For technical reasons, the fittings shall only be welded to pipes conforming to DIN 8074 and to fittings of the same pipe series, the use of other fittings being permitted if the nominal wall thickness in the jointing zone of the components is the same.

2 Dimensions and designation

Fittings are not expected to conform to the designs illustrated here; compliance is only required in the case of the dimensions specified.


The limit angular deviations shall be $\pm 2^\circ$.

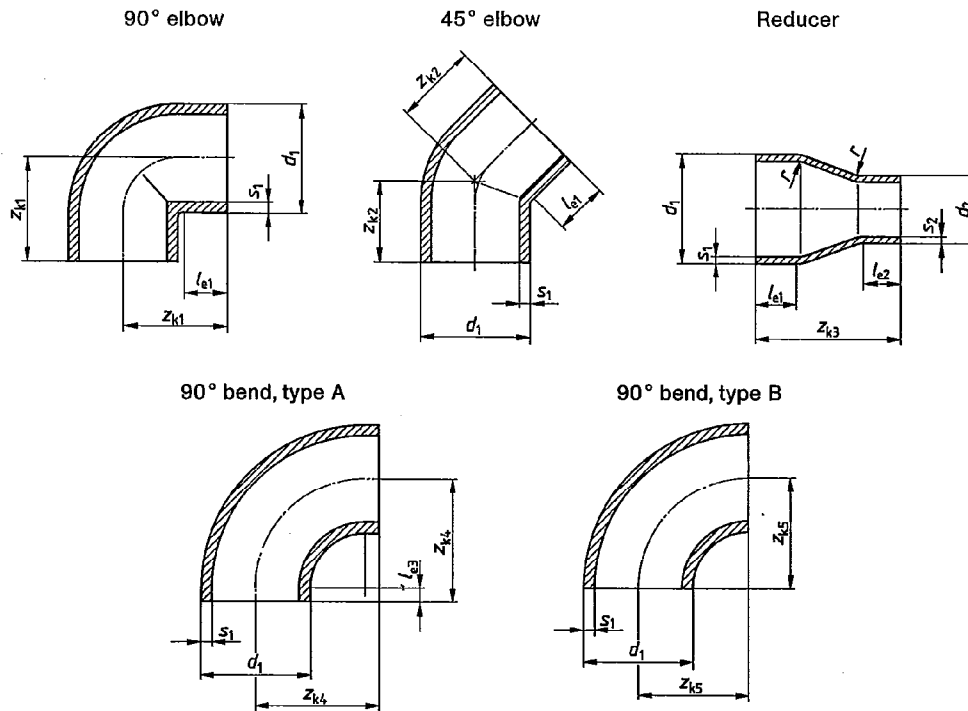

¹⁾ See DIN 16700 for definition of 'injection moulding'.

Continued on pages 2 to 4

No part of this standard may be reproduced without the prior permission of DIN Deutsches Institut für Normung e. V., Berlin. In case of doubt, the German-language original should be consulted as the authoritative text.

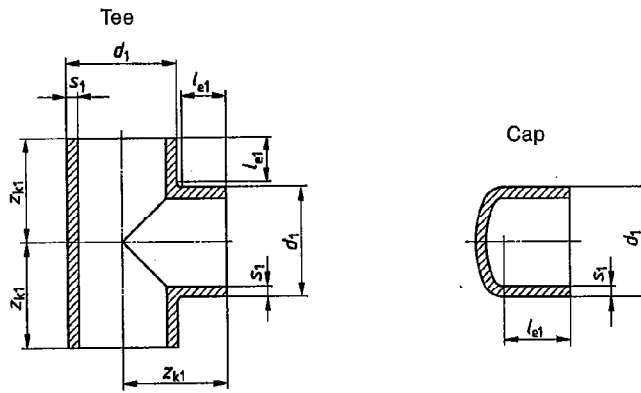

Designation of a 90° elbow as specified in this standard (6), with $d_1=63$ mm, to be joined with PE-HD pipes of pipe series 5:

Elbow DIN 16963 – 6 – 90 – 63 – 5 PE-HD

Designation of a reducer as specified in this standard (6), with $d_1=63$ mm and $d_2=50$ mm, to be joined with PE-HD pipes of pipe series 4:

Reducer DIN 16963 – 6 – 63 × 50 – 4 PE-HD

Designation of a type A 90° bend as specified in this standard (6), with $d_1=63$ mm, to be joined with PE-HD pipes of pipe series 5:

Bend DIN 16963 – 6 – 90 A – 63 – 5 PE-HD

Table 1. Dimensions of elbows, bends, tees and caps

$d_1^{2)}$	l_{e1} min.	l_{e3} min.	Wall thickness, s_1					z_{k1} min.	z_{k2} min.	z_{k4} min.	z_{k5} min.
			Pipe series								
			2 PN 3,2	3 PN 4	4 PN 6	5 PN 10	6 PN 16				
20	5	2	-	-			20	14	21	19	
25	6	3	-	-			25	17	26	23	
32	8	4	-	-			32	22	34	30	
40	10	5	-				40	26	43	38	
50	12	5					50	33	53	48	
63	16	5					63	41	66	61	
75	19	6					75	49	78	72	
90	22	6					90	57	93	87	
110	28	8					110	70	115	107	
125	32	8					125	79	130	122	
140	35	8					140	88	145	137	
160	40	8					145	95	165	157	
180	45	8					155	100	184	176	
200	50	8					170	110	204	196	
225	55	10					220	140	231	-	
250	60	10					220	156	256	-	
280	70	10					250	175	286	-	
315	80	10					275	198	261	-	

See DIN 8074 for wall thickness and associated limit deviations.

²⁾ Identical with the outside diameters (and limit deviations) specified in DIN 8074.

Table 2. Reducer

Reducer diameters		Wall thicknesses, s_1 and s_2								
$d_1^{2)}$	$d_2^{2)}$	l_{e1} min.	l_{e2} min.	r min.	Pipe series					min.
					2 PN 3,2	3 PN 4	4 PN 6	6 PN 10	s_{k3} PN 16	
25	20	6	5	5	-	-				30
32	20	8	5	5	-	-				30
32	25	8	6	5	-	-				30
40	20	10	5	5	-	-				40
40	25	10	6	5	-	-				40
40	32	10	8	5	-	-				40
50	25	12	6	5	-	-				50
50	32	12	8	5	-	-				50
50	40	12	10	5	-	-				50
63	32	16	8	8	-	-				60
63	40	16	10	8	-	-				60
63	50	16	12	8	-	-				60
75	40	19	10	8	-	-				65
75	50	19	12	8	-	-				65
75	63	19	16	8	-	-				65
90	50	22	12	8	-	-				75
90	63	22	16	8	-	-				75
90	75	22	19	8	-	-				75
110	63	28	16	10	-	-				90
110	75	28	19	10	-	-				90
110	90	28	22	10	-	-				90
125	75	32	19	10	-	-				100
125	90	32	22	10	-	-				100
125	110	32	28	10	-	-				100
140	90	35	22	10	-	-				110
140	110	35	28	10	-	-				110
140	125	35	32	10	-	-				110
160	110	40	28	10	-	-				120
160	125	40	32	10	-	-				120
160	140	40	35	10	-	-				120
180	125	45	32	15	-	-				130
180	140	45	35	15	-	-				130
180	160	45	40	15	-	-				130
200	140	50	35	15	-	-				135
200	160	50	40	15	-	-				135
200	180	50	45	15	-	-				135
225	160	55	40	20	-	-				160
225	180	55	45	20	-	-				160
225	200	55	50	20	-	-				160
250	180	60	45	20	-	-				175
250	200	60	50	20	-	-				175
250	225	60	55	20	-	-				175
280	200	70	50	20	-	-				200
280	225	70	55	20	-	-				200
280	250	70	60	20	-	-				200
315	225	80	55	20	-	-				225
315	250	80	60	20	-	-				225
315	280	80	70	20	-	-				225

See DIN 8074 for wall thickness and associated limit deviations

For 2), see table 1.

Standards and other documents referred to

- DIN 1910 Part 3 Welding of plastics; processes
- DIN 8074 High-density polyethylene pipes; dimensions
- DIN 16700 Plastics; moulding technique; processing methods and tools; concepts
- DIN 16963 Part 5 Pipe joint assemblies and fittings for polyethylene (PE-HD) pressure pipes; general quality requirements and testing
- DVS 2207 Part 1³⁾ *Schweißen von thermoplastischen Kunststoffen; PE hart (Polyethylen hart); Röhre und Rohrleitungstelle für Gas- und Wasserleitungen* (Welding of thermoplastics; unplasticized polyethylene (PE); pipes and fittings for gas and water conduits)

Other relevant standards

- DIN 8075 High-density polyethylene (PE-HD) pipes; general quality requirements and testing
- DIN 16963 Part 1 Pipe joint assemblies and fittings for types 1 and 2 high-density polyethylene (PE-HD) pressure pipes; gusseted bends for butt welding; dimensions
- DIN 16963 Part 2 Pipe joint assemblies and fittings for types 1 and 2 high-density polyethylene (PE-HD) pressure pipes; gusseted tees and branches produced by necking, for butt welding; dimensions
- DIN 16963 Part 3 Pipe joint assemblies and fittings for types 1 and 2 high-density polyethylene (PE-HD) pressure pipes; pipe bends for butt welding; dimensions
- DIN 16963 Part 4 (at present at the stage of draft) Pipe joint assemblies and fittings for types 1 and 2 high-density polyethylene (PE-HD) pressure pipes; nipples for heated tool butt welding, flanges and gaskets; dimensions
- DIN 16963 Part 7 Pipe joint assemblies and fittings for types 1 and 2 high-density polyethylene (PE-HD) pressure pipes; injection-moulded electro fusion fittings; dimensions
- DIN 16963 Part 8 Pipe joint assemblies and fittings for types 1 and 2 high-density polyethylene (PE-HD) pressure pipes; injection-moulded elbows for socket welding; dimensions
- DIN 16963 Part 9 Pipe joint assemblies and fittings for types 1 and 2 high-density polyethylene (PE-HD) pressure pipes; injection-moulded tees for socket welding; dimensions
- DIN 16963 Part 10 Pipe joint assemblies and fittings for types 1 and 2 high-density polyethylene (PE-HD) pressure pipes; injection-moulded sockets and caps for socket welding; dimensions
- DIN 16963 Part 11 Pipe joint assemblies and fittings for types 1 and 2 high-density polyethylene (PE-HD) pressure pipes; bushes, flanges and gaskets for socket welding; dimensions
- DIN 16963 Part 13 Pipe joint assemblies and fittings for types 1 and 2 high-density polyethylene (PE-HD) pressure pipes; turned and pressed reducers for butt welding; dimensions
- DIN 16963 Part 14 Pipe joint assemblies and fittings for types 1 and 2 high-density polyethylene (PE-HD) pressure pipes; injection-moulded reducers and nipples for socket welding; dimensions
- DIN 16963 Part 15 Pipe joint assemblies and fittings for high-density polyethylene (PE-HD) pressure pipes; pipe couplings; dimensions

Explanatory notes

Joining of PE-HD fittings with each other or with PP pipes as specified in DIN 8074 by welding shall be effected with the aid of welding fixtures. The dimensions of such fittings have been specified so as to permit them to be properly held in these fixtures. By virtue of their design, type A and B 90° bends cannot properly be held in normal welding fixtures; therefore, use of special clamping devices is required.

International Patent Classification

F 16 L 47/00

E 03 B 7/00

³⁾ Obtainable from *DVS Verlag GmbH*, Postfach 27 25, D-4000 Düsseldorf 1.